

This is a pre print version of the following article:

Designing epoxy viscosity for optimal mechanical performance of coated Glass Textile Reinforced Mortar (GTRM) composites / Signorini, C.; Nobili, A.; Sola, A.; Messori, M.. - In: CONSTRUCTION AND BUILDING MATERIALS. - ISSN 0950-0618. - 233:(2020), pp. 117325-117325. [10.1016/j.conbuildmat.2019.117325]

*Terms of use:*

The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. For all terms of use and more information see the publisher's website.

19/04/2024 23:07

(Article begins on next page)

# Designing epoxy viscosity for optimal mechanical performance of coated Glass Textile Reinforced Mortar (GTRM) composites

Cesare Signorini<sup>a,b,\*</sup>, Andrea Nobili<sup>c</sup>, Antonella Sola<sup>c</sup>, Massimo Messori<sup>c</sup>

<sup>a</sup>*Dipartimento di Scienze e Metodi dell'Ingegneria, via Amendola 2, 42122 Reggio Emilia, Italy*

<sup>b</sup>*Dipartimento di Economia, Scienze e Diritto, Via Consiglio dei Sessanta 99, 47899 Dogana, Republic of San Marino*

<sup>c</sup>*Dipartimento di Ingegneria Enzo Ferrari, via Vivarelli 10, 41125 Modena, Italy*

---

## Abstract

Preliminary epoxy coating of the reinforcing fabric provides an effective approach for improving matrix-to-fabric strength in inorganic matrix composites. We investigate the effect of epoxy resin dilution in acetone on uni-axial tensile performance of coated alkali-resistant (AR) glass fabric embedded in a lime-based matrix. Remarkably, it is found that dilution has a mixed effect on performance and this trend is consistently retrieved for strength, ductility and energy dissipation. Indeed, performance initially decays and then it suddenly raises to a level close to or even exceeding that of the undiluted specimens. It is postulated that this behaviour is caused by resin viscosity, that falls off exponentially with the dilution degree. Once a viscosity threshold is breached, epoxy is capable of penetrating inside the yarn and thereby prevents telescopic failure, that is the sliding of the outer over the inner glass filaments. Furthermore, the interphase surface area increases dramatically and this enhances performance and narrows scattering. Besides, optimal viscosity is reached at an unexpectedly high dilution degree, whence material cost is significantly reduced. A cost-to-performance comparison of common strengthening technologies is presented, which shows that diluted epoxy composites score comparably to FRPs. It is

---

\*Corresponding author

*Email address:* [cesare.signorini@unimore.it](mailto:cesare.signorini@unimore.it) (Cesare Signorini)

concluded that epoxy coating optimization plays an important role in designing inorganic matrix composites.

*Keywords:* TRM, Epoxy coating, dilution, optimization, viscosity

---

## 1 **1. Introduction**

2 Inorganic matrix composites, such as Textile Reinforced Mortar/Concrete  
3 (TRM/TRC), **Fibre Reinforced Cementitious Matrix (FRCM) and Inorganic**  
4 **Matrix-Grid (IMG)** are being extensively investigated as promising alternatives  
5 to the now traditional Fabric Reinforced Polymers (FRPs) [1]. Indeed, they  
6 present well-known advantages over FRPs, such as thermal stability [2], en-  
7 hanced durability [3, 4], reversibility of intervention and affinity to traditional  
8 building materials [5, 6]. Besides, from an environmental standpoint, the in-  
9 organic binder is certainly preferred over the organic matrix because it may  
10 be easily repaired, strengthened or, eventually, recycled [7, 8]. On the other  
11 hand, inorganic binders offer weaker mechanical response and, therefore, they  
12 are unable to exploit the remarkable mechanical properties of the reinforcing  
13 fabric. As a result, failure is fragile and inconsistent, for it mainly occurs by  
14 internal delamination at the fabric-to-matrix interface [9]. On top of this, the  
15 inorganic binder is coarse and viscous and therefore it is unable to penetrate  
16 the small voids between the fabric filaments within the yarns. This leads to  
17 the possibility of telescopic failure, that occurs when the outer filaments (the  
18 so-called sleeve) adhere to the binder and yet they are capable of sliding over  
19 the inner filaments (the core). Although this failure mode is more ductile, for  
20 it is friction dominated, it still prevents the composite to reach its potential  
21 performance [10, 8].

22 Several techniques have been proposed to address the limits inherent to  
23 inorganic-based composites and, among these, fabric coating certainly appears  
24 as one of the most promising [11, 12, 13, 14]. In particular, epoxy coating offers  
25 obvious advantages for it draws on the vast body of knowledge gained with FRP  
26 systems and, at the same time, minimizes the impact of the organic component.

27 Remarkably, very few contributions are available in the literature concerning the  
28 actual role of epoxy resin at the fabric-to-matrix interface. Besides, for the most  
29 part, they report on the effect of the coating, with little investigation on the  
30 coating technique and formulation, nor on the action mechanisms. In [15], the  
31 effect of epoxy coating on tensile, pull-out and water absorption performance of  
32 TRC is presented. In [16], epoxy is applied at the lamination stage (wet coat-  
33 ing) to create, together with sand, a thick intermediate layer between the carbon  
34 fabric and the inorganic matrix. In [10], two formulations for the epoxy coat-  
35 ing are adopted which produce different coating thickness and this is found to  
36 strongly affect performance. In [2], epoxy coated TRM composites are exposed  
37 to high temperatures and mechanical performance appears little impaired until  
38 temperatures in excess of 200 °C are reached. In general, the details of the me-  
39 chanical action of the epoxy coating on the interphase strength remain unclear  
40 and likewise so for the optimal formulation and application strategies. Most  
41 importantly, we still need to understand how much we can benefit from epoxy  
42 coating in terms of mechanical performance and how well we fare in compar-  
43 ison with competing technologies. In this paper, following a simplest possible  
44 approach, we consider coating by a single epoxy resin with different degrees of  
45 dilution in acetone. The aim is to resolve the effect of interphase strengthening  
46 as opposed to yarn penetration. It is found that dilution weakens the inter-  
47 phase until interpenetration suddenly takes place and undiluted performance  
48 is restored or even surpassed. Finally, we present a simple cost effectiveness  
49 analysis according to which the optimal epoxy dilution places coated G-TRM  
50 alongside FRP in terms of cost-to-performance ratio.

## 51 **2. Materials and methods**

### 52 *2.1. Materials*

53 A commercially available premixed lime-based mortar (Kerakoll Spa, Geo-  
54 calce Fino<sup>®</sup>) is considered as the embedding medium for the reinforcing fabric;  
55 its nominal properties, as given by the manufacturer, are gathered in Table 1.

Table 1: Mortar properties (Kerakoll Spa, Geocalce Fino<sup>®</sup>), as given by the manufacturer

Characteristic	Unit	Value
Actual setting water content	%	22 ÷ 23
Final density	g/cm <sup>3</sup>	1.58
Min. compression strength after 28 days	MPa	15.0
Min. flexural strength after 28 days (EN 196/1)	MPa	5.0
Min. support adhesion strength after 28 days	MPa	1.0
Aggregate maximum size	mm	1.4
Compression elastic modulus (EN 13412)	GPa	9.0

Table 2: AR-glass fabric properties.

Characteristic	Unit	Value
Yarn count	tex <sup>(*)</sup>	1200
Net specific weight per unit fabric area	g/mm <sup>2</sup>	300
Fabric specific weight	g/cm <sup>3</sup>	2.50
Grid spacing (square grid)	mm	12
Equivalent thickness, $t_f$	mm	0.06
Ultimate strength along warp (with epoxy)	MPa	1200
Ultimate elongation along warp	mstrain <sup>(**)</sup>	20
Elastic modulus	GPa	74

(\*) tex = g/km; (\*\*) 1 mstrain =  $10^{-3}$  mm/mm.

56 Mortar characterization, through flexural and compression tests, is described in  
 57 Section 3.1.

58 A thermo-welded balanced open-square grid AR-glass woven fabric (Fibre  
 59 Net SpA) is employed as the reinforcing phase. The zirconium oxide (ZrO<sub>2</sub>)  
 60 sizing of the fibres ensures stability in the alkaline environment. The main  
 61 geometrical and mechanical properties of this fabric, as declared by the manu-  
 62 facturer, are reported in Table 2. We point out that, for better comparison, the  
 63 same mortar and reinforcing fabric as in [10, 2] are considered.

#### 64 2.1.1. Fabric coating

65 As detailed in Messori et al. [10], AR-glass fabric is preliminarily treated  
 66 with a coupling agent, to enhance chemical compatibility with the epoxy coat-  
 67 ing. A 2% vol. aqueous solution of (3-Aminopropyl) triethoxysilane (99%,  
 68 Sigma-Aldrich) is prepared in a covered beaker and mixed on a magnetic stir-  
 69 rer for 15 min. Cut-to-size fabric sheets are immersed in this silane solution

Table 3: Epoxy coating compositions (normalized to 100 g of DER + acetone) and measurement of the actual polymer content ( $w_r$ ) with respect to the matrix ( $w_m$ ).

Dilution degree	D.E.R. [g]	Acetone [g]	DETA [g]	Resin [g]	$w_r/w_m$ [%]
0%	100	0	11.9	111.9	4.68
10%	90	10	10.7	100.7	4.31
25%	75	25	8.9	84.9	3.50
50%	50	50	6.0	56.0	1.33
75%	25	75	3.0	28.0	0.62
90%	10	90	1.2	11.2	0.23

70 for 1 min and then left to dry naturally at ambient temperature. Successively,  
71 the functionalized fabric is coated with epoxy resin obtained from high-purity  
72 bisphenol A diglycidylether (D.E.R. 332, DOW Chemicals). The aliphatic hard-  
73 ener diethylenetriamine (DETA 99%, Alfa-Aesar) is adopted as curing agent.  
74 Alongside the undiluted epoxy, 6 dilution degrees are considered for the epoxy  
75 precursor and, to this purpose, technical acetone ( $(\text{CH}_3)_2\text{CO}$ , Incofar Srl) is  
76 adopted at 10, 25, 50, 75 and 90% weight ratios. To reduce the viscosity of  
77 the solution, D.E.R. is mixed with acetone on a magnetic stirrer at 50 °C. The  
78 solution is subjected to ultrasonication for 5 min to promote homogenization.  
79 Finally, the curing agent is added and the solution is mixed for at least 15 min  
80 or until complete homogenization is reached. Successively, fabric sheets are im-  
81 mersed in the epoxy resin and than laid to harden for 7 days on a polypropylene  
82 support at ambient temperature. All the fabric sheets are weighted before and  
83 after coating in order to determine the polymer weight fraction in the finished  
84 composite, as listed in Table 3, which also summarizes the dilution degrees in-  
85 vestigated in the present work. It is noteworthy that the total polymer weight  
86 does not exceed the threshold of 5%wt. defined by the most popular guidelines  
87 [17] and sharply decay around a dilution degree of 50%, reaching a negligible  
88 value ( $< 1.5\%$ ). Besides, the polymer weight fraction does not correlate linearly  
89 with the dilution degree. Such evidence is in accordance with what found out  
90 in Section 4.

91 *2.1.2. Specimen manufacturing*

92 Following Annex A of ICC AC 434 [18], 1-ply rectangular coupons are cast  
93 on an individual basis, to avoid cutting from a larger sheet. The manufacturing  
94 process takes place through the following stages (see [4, 6, 13] for further details):

- 95 • Assembling of the dismantable formwork: the first set of equally-spaced  
96 3-mm-thick constraining laths is placed onto a polyethylene support and  
97 silicone oil is applied;
- 98 • A first layer of natural hydraulic lime (NHL) mortar is laid in between the  
99 laths by manual wet lay-up and levelled on top with a scraper;
- 100 • Cut-to-size epoxy coated fabric sheets are laid and gently pressed onto the  
101 fresh mortar, Fig.1(a);
- 102 • The second set of 3-mm-thick constraining laths is attached on top of the  
103 first to provide guidance for the correct placing of the fabric as well as for  
104 a second layer of mortar;
- 105 • Mortar is laid in between the laths and levelled up, Fig.1(b).

106 Specimens are left moist-curing in a polypropylene bag for 7 days and then  
107 stripped from the formwork. Formwork disassembling facilitates the process of  
108 stripping. Successively, curing takes place in the laboratory environment for  
109 further 50 days. 7 days prior to mechanical testing, 100 mm-long G-FRP tabs  
110 are glued at the specimen ends to accommodate the gripping system, Fig.1(c).

111 **3. Experimental investigation**

112 *3.1. Mortar characterization*

113 Three-point bending (3PB) tests are carried out on mortar prisms, according  
114 to the guidelines UNI EN 1015-07 [19], to precisely assess the mechanical per-  
115 formance of the lime-based mortar. Consequently, mortar specimens are cast in  
116 a  $40 \times 40 \times 160$  mm stainless steel mold and vibro-compacted. Specimen prisms  
117 are subjected to 7 day moist-curing and then stored to cure in a Memmert HP10

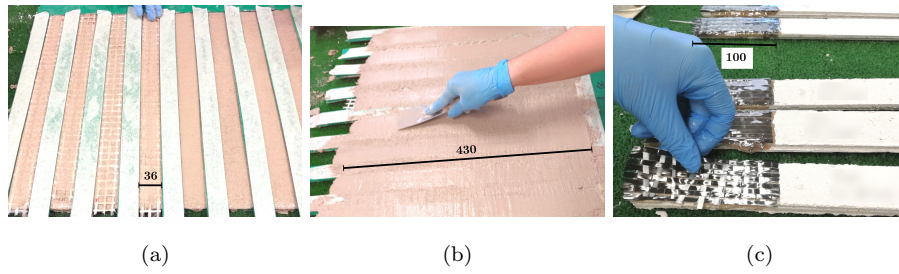


Figure 1: Specimen manufacturing protocol: (a) epoxy coated fabric sheets are placed onto the first layer of mortar, (b) application of the second layer of mortar, (c) C-FRP end tabs are glued to the specimens. *Quotes are in mm.*

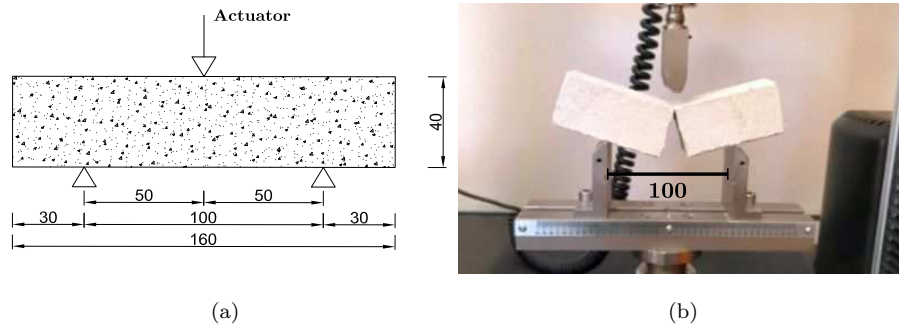


Figure 2: Three-point bending (3PB) test for mortar characterization: test geometry (a), test set-up and failed specimen (b). *Quotes are in mm.*



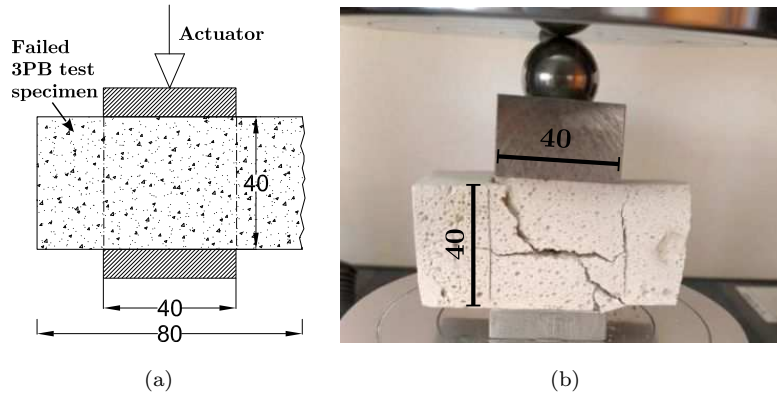


Figure 3: Compression test set-up (a) and failed specimen (b). *Quotes are in mm.*

118 climatic chamber at 65% relative humidity (RH) for further 21 days. Tests are  
 119 performed through a Universal Testing Machine (UTM) at a nominal displace-  
 120 ment rate of 1 mm/min (equivalent to  $50 \div 100 \text{ Ns}^{-1}$ ). The test geometry and  
 121 set-up are shown in Fig.2.

122 Monotonic compression tests are performed on failed specimens after 3PB  
 123 (Fig.3): either specimen end is compressed between two  $40 \times 40$  mm plates at a  
 124 fixed displacement rate of 1 mm/min (equivalent to  $50 \div 500 \text{ Ns}^{-1}$ ). To rule out  
 125 unwarranted bending effects which may arise owing to geometric irregularities  
 126 in the specimen, a steel ball is placed right under the top steel plate of the UTM,  
 127 see Fig.3. Flexural and compression ultimate strength and elastic moduli are  
 128 obtained from the experimental curves. At least 6 specimens are tested both in  
 129 compression and in flexure.

### 130 3.2. Uni-axial tensile tests

131 Uni-axial tensile tests are performed according to ICC AC434 [18] in a UTM  
 132 equipped with a 30 kN load cell. Wedge grips act on the end tabs and loading is  
 133 applied by means of friction; wedges ensure adequate lateral pressure to avoid  
 134 slippage between the specimen and the clamp (see [20] for a discussion on the  
 135 effect of different clamping systems). A spherical hinge allows for self-alignment  
 136 of the specimen and minimizes bending effects. Tests are conducted at a fixed  
 137 strain rate of 2 mstrain/min ( $2 \cdot 10^{-3} \text{ min}^{-1}$ ), as prescribed in [21]. As in



Figure 4: Rheometer test set-up

138 standard practice, stress and strain obtained from the test are referred to the  
 139 fabric cross-section,  $A_f$ , and to the gauge length,  $L_g = 230$  mm,

$$\sigma = \frac{P}{A_f}, \quad \varepsilon = \frac{\delta}{L_g}. \quad (1)$$

140 Here,  $P$  and  $\delta$  are the load and the corresponding displacement, as measured  
 141 by the UTM and corrected by DIC to eliminate wedge grip elongation (see also  
 142 [4]).

### 143 3.3. Digital Image Correlation data post-processing

144 Tensile tests are monitored by Digital Image Correlation (DIC) with a 3  
 145 megapixel stereoscopic Dantec Dynamics optical system (Q-400). DIC allows  
 146 to fine measure the actual displacement field of the specimen surface, that is  
 147 previously sprayed with a fine black speckled pattern onto a white background.

### 148 3.4. Optical and electron scanning microscopy

149 Optical investigation at 35x magnification is performed in a Leica EZ4D  
 150 stereo-microscope to qualitatively assess the coating distribution and its effect  
 151 on interphase adhesion. A scanning electron microscope (SEM) Quanta-200 (Fei  
 152 Company, The Netherlands) is also employed.

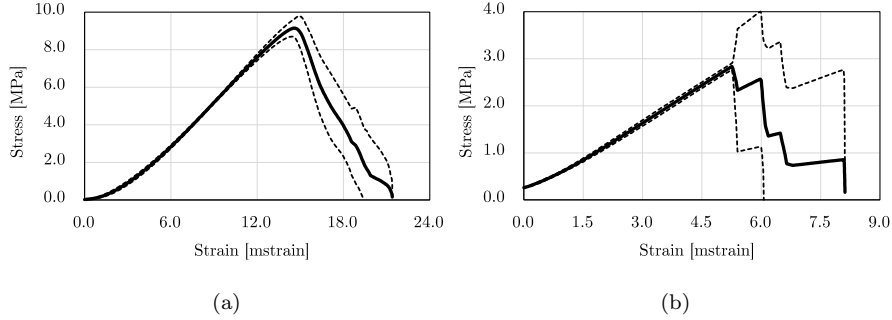


Figure 5: Mean stress-strain curve with  $\pm 1$  standard deviation bands for compression (a) and bending (b) of lime mortar prisms. (1 mstrain =  $10^{-3}$  mm/mm)

### 153 3.5. Rheometer analysis

154 Resin viscosity is measured, for different dilution degrees, through a HAAKE  
 155 RS100 Rheostress rheometer (Fig.4), that applies to the fluid a nominal tangen-  
 156 tial stress,  $\tau$ , at constant temperature ( $37 \pm 1$ )°C. This temperature is chosen  
 157 as to represent the actual conditions of fabric impregnation. The test program  
 158 consists of an ascending ramp plus a descending ramp for the applied torque.

## 159 4. Results

### 160 4.1. Mortar characterization

161 The mean stress-strain curves for compression and bending of lime mortar  
 162 prisms are reported in Figs.5(a) and (b), respectively. Data scattering is pro-  
 163 vided by  $\pm 1$  standard deviation bands and it appears remarkably narrow for  
 164 both compression and bending. Table 4 gathers the mean value of the mortar  
 165 ultimate strength,  $\mu(f)$ , as well as of the secant modulus,  $\mu(E)$ , together with  
 166 the relevant standard deviation,  $\zeta(\cdot)$ , and coefficient of variation,  $CV(\cdot)$ . The  
 167 characteristic value  $(\cdot)_k$  is evaluated as for a normal distribution (with the so-  
 168 called "2-sigma-rule", used in the construction of approximate 95% confidence  
 169 intervals [22])

$$(\cdot)_k = \mu(\cdot) - 1.96 \zeta(\cdot). \quad (2)$$

170 The elastic modulus is determined from the stress-strain curve as the slope  
 171 of the secant line passing through  $(\sigma_{0.6}, \varepsilon_{0.6})$  and  $(\sigma_{0.9}, \varepsilon_{0.9})$ , that are the stress-

<b>Characteristic Unit</b>	$\mu(\cdot)$ [MPa]	$\varsigma(\cdot)$ [MPa]	$CV(\cdot)$ [%]	$(\cdot)_k$ (Eq.(2)) [MPa]
Compressive strength, $f_c$	9.2	0.5	5.4	8.2
Young Modulus, $E_{c,s}$ (Eq.(3))	802	41	5.1	723
Flexural strength, $f_f$	3.4	0.6	17.6	2.3
Flexural modulus, $E_{f,s}$ (Eq.(3))	539	13	2.4	512

Table 4: Mechanical characterization of the lime mortar according to [19].  $\mu(f)$ ,  $\varsigma(f)$  and  $(f)_k$  are the mean, the standard deviation and the characteristic value of the (assumed normally distributed) stochastic variable  $f$  and they are connected through Eq.(2).  $CV = \varsigma/\mu$  is the coefficient of variation

172 strain points at 60% and 90% of the ultimate strength [23]

$$E = \frac{\sigma_{0.9} - \sigma_{0.6}}{\varepsilon_{0.9} - \varepsilon_{0.6}}. \quad (3)$$

#### 173 4.2. Uni-axial tensile tests

174 Fig.6 presents the mean stress-strain curve for each coating group alongside  
175 two reference curves expressing the mean performance in the uncoated and in  
176 the undiluted (alias 0% diluted) epoxy group (the latter is taken from [10]).  
177 Remarkably, it appears that epoxy dilution in acetone little impairs the mean  
178 mechanical performance, which remains way superior to that of the uncoated  
179 group, particularly in terms of ductility. Further, most unexpectedly, perfor-  
180 mance is not a monotonic decreasing function of the dilution degree and, after  
181 an initial descending trend, it raises again and it reaches or even exceeds the  
182 undiluted performance.

183 To take a better insight into this unexpected behaviour, Fig.7 presents the  
184 mean ultimate tensile strength (UTS) and strain for all groups alongside  $\pm 1$   
185 standard deviation bars. Looking at this figure, two interesting observations  
186 can be made:

- 187 1. the mean ultimate performance is a decreasing/increasing/decreasing func-  
188 tion of epoxy dilution, which attains a local minimum at 10 ÷ 25%-dilution  
189 and then raises up to a local maximum that occurs at 75% for strength  
190 and at 50% for strain;

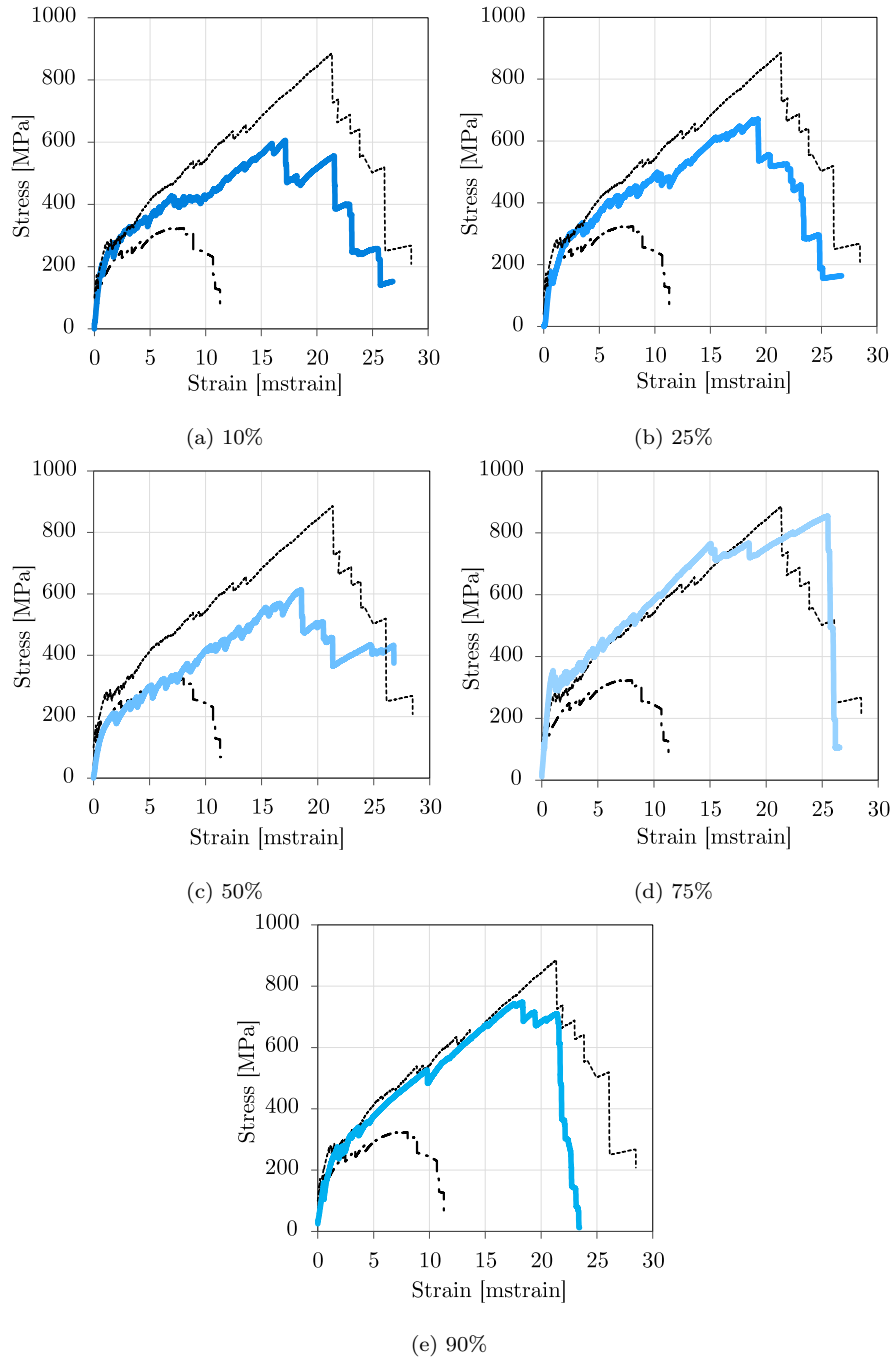


Figure 6: Mean stress-strain curves obtained in uni-axial tension of epoxy-coated G-TRM coupons for different dilution degrees (blue, solid lines), compared to the uncoated (black, dash-dotted lines) and to the undiluted (black, fine dashed lines) groups [24]. (1 mstrain =  $10^{-3}$  mm/mm)

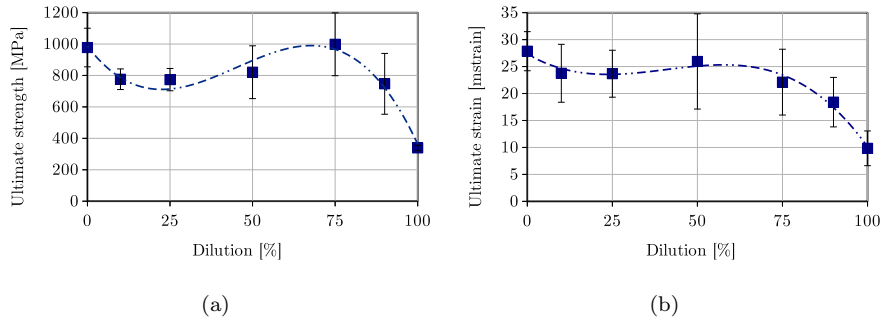


Figure 7: Mean ultimate strength (a) and strain (b) as a function of the dilution degree.  $\pm 1$  standard deviation bars and cubic curve-fits are also plotted. ( $1 \text{ mstrain} = 10^{-3} \text{ mm/mm}$ )

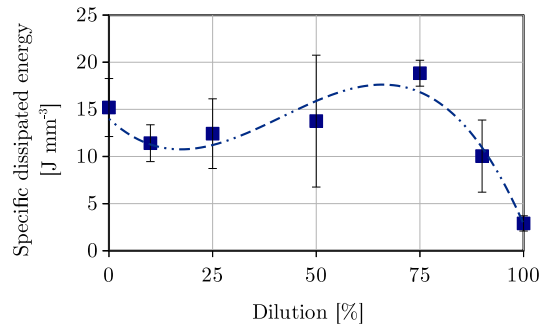


Figure 8: Mean energy dissipation per unit volume with  $\pm 1$  standard deviation bars and cubic curve fitting

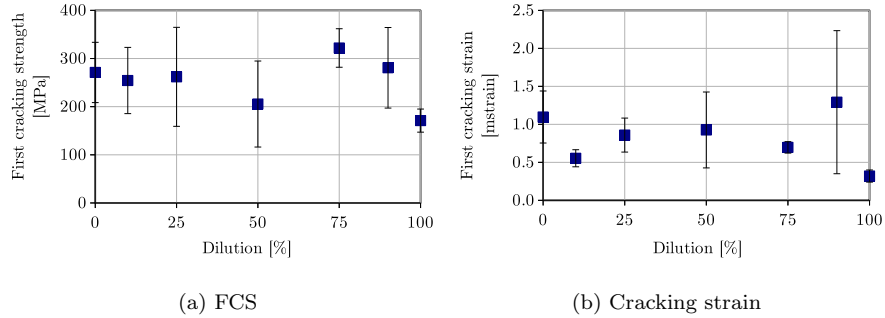


Figure 9: Mean first cracking strength (a) and strain (b) as a function of the dilution degree, with  $\pm 1$  standard deviation bars. (1 mstrain =  $10^{-3}$  mm/mm)

- 191 2. strikingly, this maximum strength appears best performing (i.e. it is an
- 192 absolute maximum), although it occurs in the presence of wider scattering
- 193 when compared to the undiluted group;
- 194 3. data scattering is not monotonic increasing either and it is relatively stable
- 195 across the groups.

196 It is important to emphasize that dilution affects strength and strain in a similar  
 197 manner, which fact is a good indication that an underlying phenomenon is  
 198 consistently being captured. Indeed, the same trend is confirmed by looking at  
 199 the dissipated energy at failure, that is evaluated as the mean, within each group,  
 200 of the area under the stress-strain curve. In this respect, Fig.8 is even more  
 201 surprising, for best performance is again associated with 75% dilution and yet  
 202 it now exceeds by more than 30% that of the undiluted group, while possessing  
 203 remarkably narrow data scattering. This behaviour seems to suggest that a  
 204 threshold dilution exists which triggers a beneficial effect on performance and  
 205 scattering. This effect competes against and eventually overcomes the expected  
 206 degradation of the epoxy coating associated with resin dilution.

207 Fig.9 plots the first cracking strength (FCS) and strain and once more it  
 208 supports the assumption that dilution has a mixed bearing on mechanical per-  
 209 formance. Here, however, the picture is less clear cut, owing to the uncertainty  
 210 that is associated with the identification of the transition point. Indeed, tran-

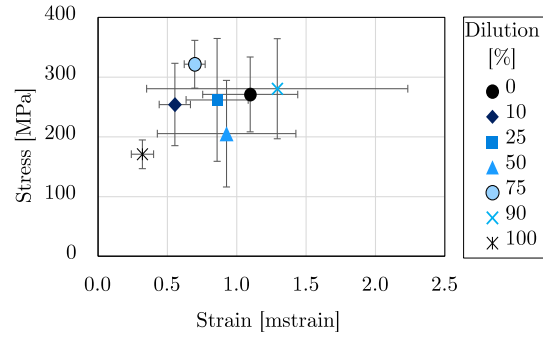


Figure 10: Transition points (TP) location as a function of the dilution degree with  $\pm 1$  standard deviation bars. (1 mstrain =  $10^{-3}$  mm/mm)

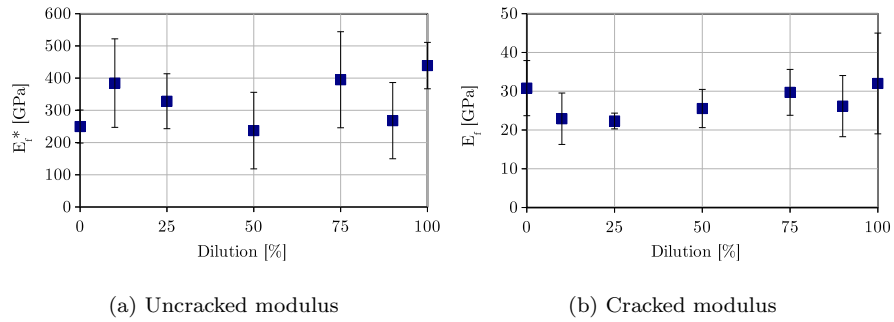


Figure 11: Mean uncracked (a) and cracked (b) moduli as a function of the dilution degree with  $\pm 1$  standard deviation bars



211 sition point location is charted in Fig.(10) and it is interesting to observe that  
212 the highest stress and the least scattering again occurs at 75% dilution. Fig.11  
213 shows the uncracked and the cracked elastic moduli, which reflects the matrix  
214 (see Tab.4) and the fabric moduli, respectively. As expected, little dependence  
215 on the dilution grade is demonstrated and yet the underlying trend can still be  
216 appreciated.

#### 217 *4.3. Optical and Scanning Electron Microscopy*

218 Fig.12 presents the outcome of optical investigation of failed specimens at  
219 35x. The effect of dilution emerges with great clarity in that individual fibres  
220 within the fabric yarn can only be appreciated at high dilution degrees, and  
221 to these fibres large mortar patches adhere. In contrast, at low dilution, fibres  
222 are deeply embedded in a sizeable lump of epoxy resin (that traps several air  
223 bubbles) to which only small mortar patches can adhere. Evidently, mortar  
224 adhesion occurs mainly at 50% and 75% dilution.

225 Along the same line and yet with greater detail, Fig.13 displays the outcome  
226 of SEM microscopy at 1000x. Indeed, at low dilution, scanty fibres emerge from  
227 the resin block which mainly surrounds the external filaments of the yarn, the  
228 so-called sleeve. To this block, scattered mortar patches adhere. In contrast,  
229 dilution reveals the glass fibres within the yarn, that the epoxy is eventually  
230 capable of penetrating. The coating thickness is substantially reduced to a  
231 thin layer to which mortar patches are diffusely attached. This adhesion is  
232 perhaps of poorer quality, yet it extends well inside the core of the fabric yarn  
233 and the surface area involved is greatly enlarged (Fig.14). Besides, telescopic  
234 failure, that is failure by sleeve filaments sliding over the core, is prevented. The  
235 dilution degree that triggers filaments penetration is the threshold level that  
236 significantly enhances mechanical response. Competing with this positive effect  
237 is the reduction of the epoxy content due to dilution, that weakens interphase  
238 adhesion and negatively affects performance. Of course, a mixed response is  
239 exhibited for intermediate dilution degrees.



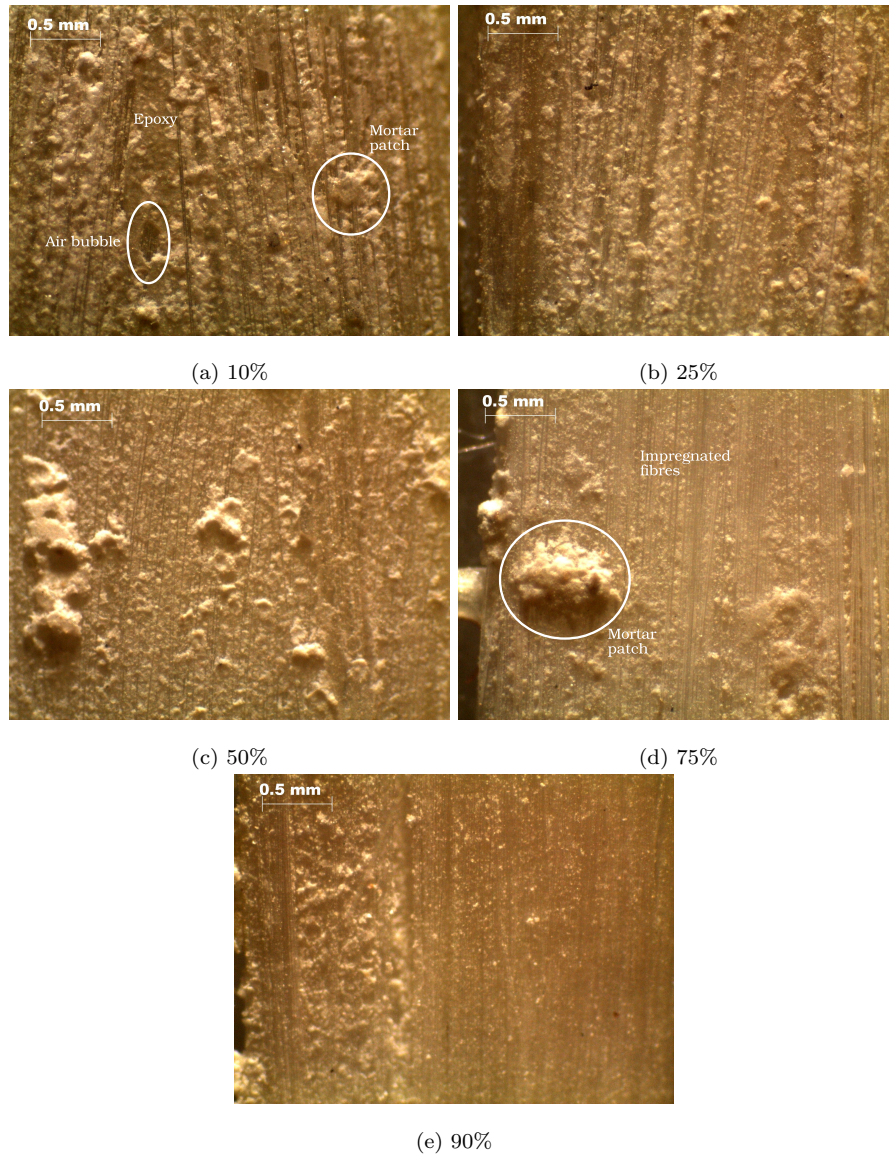


Figure 12: Optical microscopy of the fabric after failure at 35x magnification

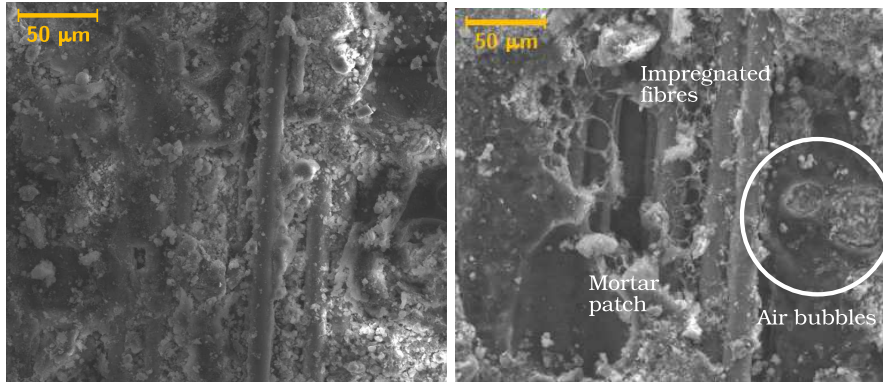


(a) 10%

(b) 25%

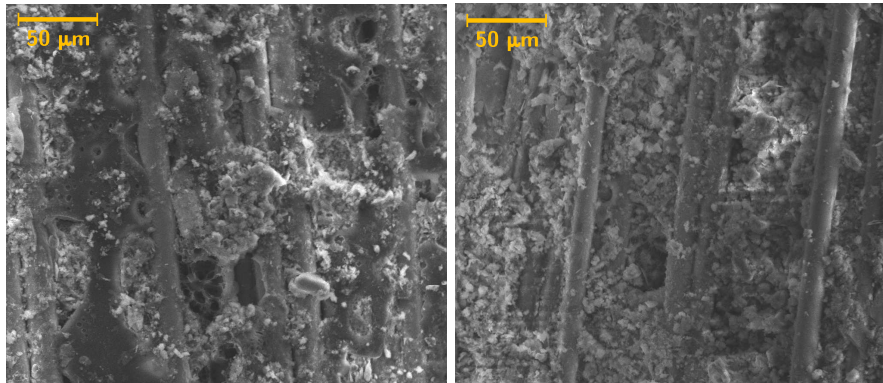

(c) 50%

(d) 75%

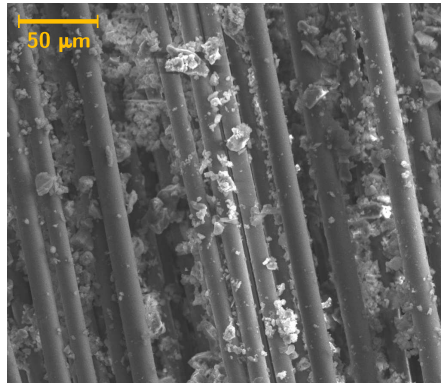

(e) 90%

Figure 13: SEM of the fabric after failure at 1000x magnification

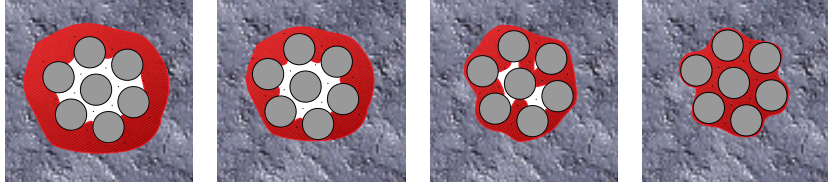


Figure 14: Penetration of the epoxy resin (red) in the voids between the filaments (gray) within the fabric yarn: dilution decreases viscosity and favours deep penetration

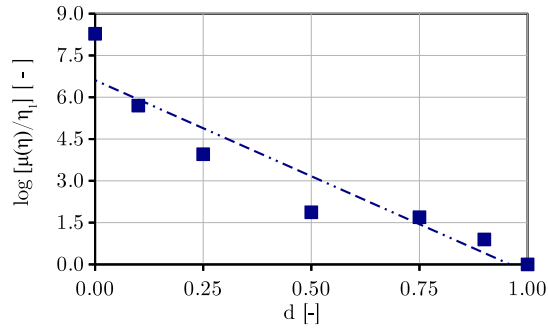


Figure 15: Viscosity measurement in logarithmic scale at 37 °C as a function of the dilution degree. An exponential curve-fit is also proposed ( $R^2 = 0.95$ )

#### 240 4.4. Viscosity curve

241 It is most striking that the beneficial effect of epoxy resin penetration in the  
 242 yarn core occurs almost suddenly and at an unexpectedly large dilution degree.  
 243 Indeed, the dilution threshold is located around 3 : 1 acetone to epoxy weight  
 244 ratio. This outcome may be traced back to the exponential decay of epoxy  
 245 viscosity as a function of acetone dilution  $d$ . Fig.15 plots the mean viscosity,  
 246  $\mu(\eta)$ , normalized to acetone viscosity  $\eta_1$ , superposed onto the exponential fit  
 247 (logarithmic scale)

$$\mu(\eta) = \eta_1 \exp[-6.613(d - 1)], \quad (4)$$

248 where  $0 \leq d \leq 1$  is the dilution degree. The viscosity at  $d = 1$  (i.e. the uncoated  
 249 group) is let equal to acetone viscosity, namely  $\eta_1 = 0.28 \text{ mPa} \cdot \text{s}$  [25]. The fit  
 250 shows good correlation ( $R^2 = 0.9518$ ).

Dilution 100d [%]	probability of exceedence [%]		
	UTS	Strain	Energy
10	1.0	7.8	1.8
25	0.4	9.8	8.4
50	8.2	30.6	31.2
75	53.6	46.2	89.2
100	4.0	0	4.2

Table 5: Permutation test results

## 251 5. Resampling analysis

252 We begin by considering the question whether the different behaviour that  
253 we see across the test groups is due to sampling or rather reflects some intrinsic  
254 variance. For this, we carry out a permutation test on the total count [26] and  
255 results are given in Tab.5. The permutation test works as follows: we compare  
256 two dilution groups, namely 0%, that is the reference group, and  $y\%$  and for this  
257 we bring them together in the set  $A_y$ . Then, we form  $N = 500$  permutations  
258 with repetition of 5 elements of  $A_y$  and, for each of these, we compute the  
259 total count (sum of the elements)  $s_k$ ,  $k = 1, \dots, 500$ . We count the number  
260 of permutations whose total count exceeds that of the reference group 0% and  
261 divide by  $N$ . We expect that, when difference is due to sampling, the total  
262 count of any permutation is located above/below the reference count 50% of  
263 the times. We see that this is never really the case for any group, although it  
264 may occasionally occur for a single characteristic. For instance, considering UTS  
265 and ultimate strain, we see that the reference group and  $y = 75\%$  dilution are  
266 statistically equivalent, yet the latter still dissipates significantly more energy  
267 than the former. We conclude that results are statistically meaningful and an  
268 underlying process is being captured.

269 Next, we carry out a resampling analysis for each dilution group and consider  
270 the statistics of 5000 permutations with repetition of the original dataset. Fig.16  
271 plot the mean UTS and ultimate elongation, normalized to the corresponding  
272 mean of the original sampling in the undiluted group, respectively  $f_0$  and  $\varepsilon_0$ ,

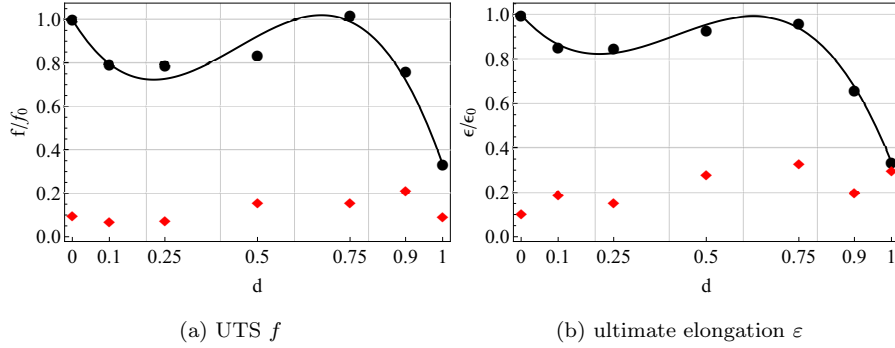


Figure 16: Resampled mean tensile ultimate strength and elongation (black, circles) with mean CV (red, diamonds) as a function of the dilution degree  $d$ , normalized to the corresponding mean of the original sample for the undiluted group, respectively  $f_0$  and  $\varepsilon_0$ . The cubic curve fit (5) is also shown

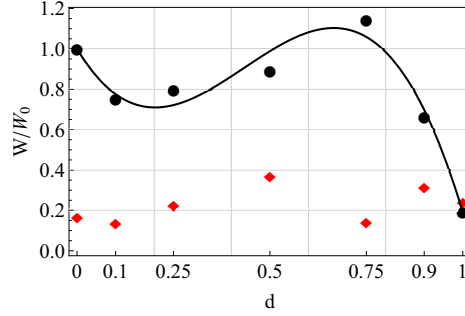


Figure 17: Resampled mean dissipated energy at failure  $W$  (black, circles) and mean CV (red, diamonds) as a function of the dilution degree, normalized to the original sample mean dissipated energy of the undiluted group,  $W_0$

273 superposed onto a cubic curve fit of the form (likewise for strain)

$$\mu(f) = f_0 [1 + (f_1 - 1)x + a_2x(x - 1) - a_3x(x^2 - 1)], \quad (5)$$

274 where  $f_1$  is the mean of the resampled uncoated group. A cubic curve-fit is  
 275 chosen because  $d \leq 1$  and any curve-fit turns into a polynomial in a Taylor sense.

276 Remarkably, upon normalization, strength and elongation follow a very similar  
 277 trend, whose resemblance supports the fact that a physical process is being  
 278 portrayed. Besides, unless a very large dilution degree is adopted, performance  
 279 rests above 80% of the uncoated group, before falling off steeply beyond 75%  
 280 dilution.

281 Figs.17 presents the resampled dissipated energy at failure  $W$ , normalized

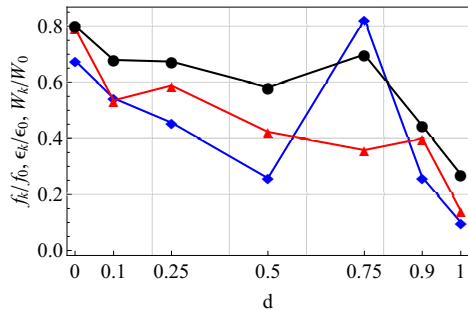


Figure 18: Resampled characteristic ultimate strength (black, circles), strain (red, triangles) and dissipated energy (blue, diamonds) as a function of the dilution degree, normalized to the corresponding mean values in the undiluted group

282 to the mean dissipated energy  $W_0$  in the original undiluted sampling, and it  
 283 shows that a 14% performance gain over the undiluted group is achieved at 75%  
 284 dilution, that is accompanied by a very small CV. This behaviour, that seems  
 285 to contrast that observed for strength and strain, may be explained noting that  
 286 these are contravariant statistical variables, in the sense that when one increases,  
 287 the other decreases and yet their "product" (i.e. the energy) remains the same.

288 With the resampling size  $N = 5000$ , the population distribution is close to  
 289 normality and we may safely consider characteristic values according to Eq.(2).  
 290 Fig.18 presents the characteristic ultimate strength, strain and dissipated en-  
 291 ergy, normalized with respect to the corresponding *mean* value in the original  
 292 sample of the undiluted group. We see that dilution has a significant negative  
 293 effect on the characteristic ultimate strain, which drops in monotonic fashion.  
 294 This is due to increasing standard deviation, see Fig.16(b). Conversely, strength  
 295 and energy recover significantly at 75% dilution to the point that they behave  
 296 almost as or better than the undiluted group. Such results support the idea  
 297 that optimizing epoxy dilution and epoxy viscosity conveys remarkable benefit  
 298 in terms of performance-to-cost efficiency.

## 299 6. A simple cost-effectiveness analysis

300 Fig.19(a) shows the total cost of raw materials per unit dissipated energy  
 301 at failure. The material cost is a decreasing function of dilution, for acetone is

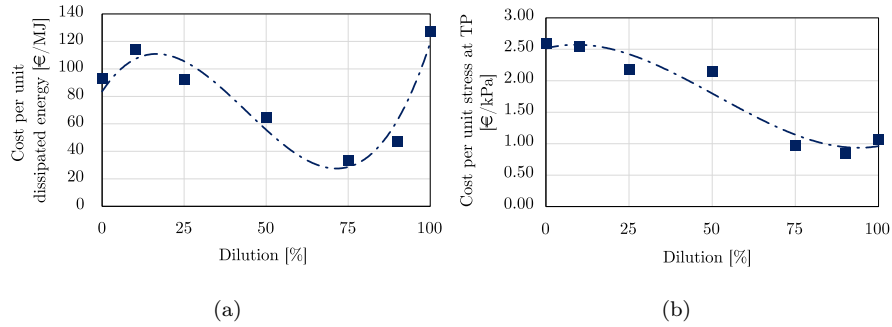


Figure 19: Mean cost per unit dissipated energy at failure (a) and per FCS (b) as a function of the dilution degree. A third-order polynomial curve-fit is also proposed.

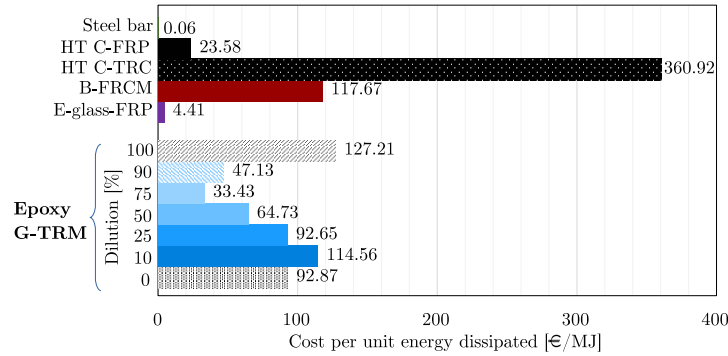


Figure 20: Comparison among strengthening and retrofitting technologies in terms of cost per unit dissipated energy (HT : high-tenacity, C : carbon, B : basalt, FRCM : fabric reinforced cementitious mortar)

302 far cheaper than epoxy, yet performance loss produces a competing trend. As  
 303 expected, an absolute optimal point is met in correspondence of 75% dilution,  
 304 where a 64% (74%) reduction in the cost-to-performance ratio is achieved, with  
 305 respect to the undiluted (uncoated) group. Within this comparison, the undi-  
 306 luted group is only 37% better performing than the uncoated group, despite the  
 307 vastly superior mechanical performance, see Fig.17. Unexpectedly, cost normal-  
 308 ization in terms of FCS leads to a monotonic decreasing function, i.e. the cost  
 309 reduction associated with dilution outweighs the performance decay in terms  
 310 of FCS, see Fig.19(b). This result, among others, may justify the marginal  
 311 diffusion of epoxy coating in the current TRM technology landscape.

312 Fig.20 presents an all-around cost-to-performance comparison among differ-



ent strengthening and retrofitting technologies, in terms of mean material cost per unit dissipated energy. Costs for FRP and steel mesh are taken from 2018 data officially provided in [27]. FRP dissipated energy is obtained referring to the mean ultimate stress-strain values, as given by [28], and restricting the analysis to the linear regime. Mechanical response of steel is assumed to follow a bilinear model, with an initial elastic response until yield, followed by a linear hardening plastic phase until failure. Data for high-tenacity (HT) carbon (C) and basalt (B)-TRC are taken from Signorini and Nobili [29]. According to Fig.20, strengthening technologies may be ranked as follows. First, steel appears to be the best performing by far, mainly in consideration of its marginal cost. This obvious result, which accounts for the large adoption of reinforced concrete, should be weighed against other design constraints, such as durability and feasibility. Then, FRP follows, in light of its low cost compared to the outstanding mechanical performance. Glass TRM comes third and we see that dilution is capable of dramatically reducing the cost-to-performance ratio to an extent that is comparable with high tenacity carbon FRP. In fact, 75% dilution produces an outstanding three-fold reduction in the cost-to-performance index compared to the undiluted group. Of course, different performance indices may be considered and costs greatly vary across countries, but the general idea that diluted epoxy coating may significantly increase the interest in TRM composites still holds. Basalt and carbon FRCM come last, although they score similarly to epoxy coated TRM. However, mechanical performance is generally little reliable in the absence of interphase strengthening [6].

## 7. Conclusions

We present the results of mechanical uni-axial traction tests on epoxy coated AR-glass Textile Reinforced Mortar (TRM) specimens. Spotlight is set on the role of the epoxy coating and its ability to penetrate the glass filaments within the yarn. To this aim, epoxy is diluted with acetone at 10, 25, 50, 75 and 90% weight ratios and performance is compared to that of undiluted and uncoated fabric. It is found that the effect of dilution is two-fold: on the one hand it de-

343 creases the interphase strength and yet, on the other hand, it decreases viscosity  
344 exponentially and therefore enhances the epoxy penetration capability. These  
345 two effects are competing and, as a result, an optimal formulation is defined.  
346 Most remarkably, filament penetration occurs at a unexpectedly high dilution  
347 degree and it takes place through a rapid surge of mechanical performance.  
348 This burst is so intense that it compensates interphase weakening, to the extent  
349 that performance gets close to or even exceeds that of the undiluted specimens.  
350 This trend consistently emerges in the first cracking strength and strain, in the  
351 energy dissipation capability, in the cracked and uncracked moduli and in the  
352 turning point location alike. Besides, a simple cost-effectiveness analysis shows  
353 that dilution leads to a very substantial material cost reduction, which places  
354 this technology on an efficiency level comparable to that of FRPs. It is con-  
355 cluded that careful engineering of the epoxy coating can significantly contribute  
356 to the improvement of the overall performance of glass TRM composites.

### 357 **Acknowledgements**

358 Prof. Marcello Romagnoli is gratefully acknowledged for his contribution in  
359 carrying out the viscosity measurements.

### 360 **Funding**

361 This work was supported by the "Enzo Ferrari" Engineering Department  
362 (University of Modena and Reggio Emilia) through "FAR dipartimentali 2019"

### 363 **Declarations of interest**

364 None.

### 365 **Data availability**

366 The raw data required to reproduce these findings are available to download  
367 from <http://dx.doi.org/10.17632/kgb7dz3yhx.1>

368 **References**

- 369 [1] V. Mechtcherine, Novel cement-based composites for the strengthening  
370 and repair of concrete structures, *Construction and Building Materials* 41  
371 (2013) 365–373.
- 372 [2] M. Messori, A. Nobili, C. Signorini, A. Sola, Effect of high temperature  
373 exposure on epoxy-coated Glass Textile Reinforced Mortar (GTRM) com-  
374 posites, *Construction and Building Materials* 212 (2019) 765–774.
- 375 [3] R. Hempel, M. Butler, S. Hempel, H. Schorn, Durability of textile rein-  
376 forced concrete, *Special Publication 244* (2007) 87–108.
- 377 [4] A. Nobili, Durability assessment of impregnated glass fabric reinforced ce-  
378 mentitious matrix (GFRCM) composites in the alkaline and saline environ-  
379 ments, *Construction and Building Materials* 105 (2016) 465–471.
- 380 [5] U. Ebead, K. Shrestha, M. Afzal, A. El Refai, A. Nanni, Effectiveness of  
381 fabric-reinforced cementitious matrix in strengthening reinforced concrete  
382 beams, *Journal of Composites for Construction* 21 (2) (2016) 04016084.
- 383 [6] A. Nobili, F. Falope, Impregnated carbon fabric-reinforced cementitious  
384 matrix composite for rehabilitation of the Finale Emilia hospital roofs: case  
385 study, *Journal of Composites for Construction* 21 (4) (2017) 05017001.
- 386 [7] C. Signorini, A. Nobili, C. Siligardi, Sustainable mineral coating of alkali-  
387 resistant glass fibres in textile-reinforced mortar composites for structural  
388 purposes, *Journal of Composite Materials* (2019) 0021998319855765.
- 389 [8] B. Mobasher, *Mechanics of fiber and textile reinforced cement composites*,  
390 CRC press, 2011.
- 391 [9] F. Carozzi, C. Poggi, Mechanical properties and debonding strength of fab-  
392 ric reinforced cementitious matrix (FRCM) systems for masonry strength-  
393 ening, *Composites Part B: Engineering* 70 (2015) 215–230.

- 394 [10] M. Messori, A. Nobili, C. Signorini, A. Sola, Mechanical performance of  
395 epoxy coated AR-glass fabric Textile Reinforced Mortar: Influence of coat-  
396 ing thickness and formulation, *Composites Part B: Engineering* 149 (2018)  
397 135–143.
- 398 [11] I. Van de Weyenberg, J. Ivens, A. De Coster, B. Kino, E. Baetens, I. Ver-  
399 poest, Influence of processing and chemical treatment of flax fibres on their  
400 composites, *Composites Science and Technology* 63 (9) (2003) 1241–1246.
- 401 [12] C. Scheffler, S. Gao, R. Plonka, E. Mäder, S. Hempel, M. Butler,  
402 V. Mechtcherine, Interphase modification of alkali-resistant glass fibres and  
403 carbon fibres for Textile Reinforced Concrete II: Water adsorption and  
404 composite interphases, *Composites Science and Technology* 69 (7-8) (2009)  
405 905–912.
- 406 [13] C. Signorini, A. Nobili, E. C. Gonzalez, C. Siligardi, Silica coating for  
407 interphase bond enhancement of carbon and AR-Glass Textile Reinforced  
408 Mortar (TRM), *Composites Part B: Engineering* 141 (2018) 191–202.
- 409 [14] C. Signorini, A. Sola, A. Nobili, C. Siligardi, Lime-cement tex-  
410 tile reinforced mortar (TRM) with modified interphase, *The Jour-  
411 nal of Applied Biomaterials and Functional Materials* 17 (1) (2019).  
412 doi:10.1177/2280800019827823.
- 413 [15] D. Dvorkin, A. Poursaei, A. Peled, W. Weiss, Influence of bundle coating  
414 on the tensile behavior, bonding, cracking and fluid transport of fabric  
415 cement-based composites, *Cement and Concrete Composites* 42 (2013) 9–  
416 19.
- 417 [16] J. Donnini, V. Corinaldesi, A. Nanni, Mechanical properties of form us-  
418 ing carbon fabrics with different coating treatments, *Composites Part B:  
419 Engineering* 88 (2016) 220–228.
- 420 [17] ACI 549.4R-13, Guide to Design and Construction of Externally Bonded  
421 Fabric-Reinforced Cementitious Matrix (FRCM) Systems for Repair and

- 422 Strengthening Concrete and Masonry Structures, American Concrete In-  
423 stitute, 2013.
- 424 [18] ICC-Evaluation Service, Acceptance criteria for masonry and concrete  
425 strengthening using fiber-reinforced cementitious matrix (FRCM) compos-  
426 ite systems (AC434), Whittier, CA (2013).
- 427 [19] UNI EN 1015-11: Methods of test for mortar for masonry – Part 11: De-  
428 termination of flexural and compressive strength of hardened mortar.
- 429 [20] J. Hartig, F. Jesse, K. Schicktanz, U. Häußler-Combe, Influence of ex-  
430 perimental setups on the apparent uniaxial tensile load-bearing capacity  
431 of textile reinforced concrete specimens, *Materials and Structures* 45 (3)  
432 (2012) 433–446.
- 433 [21] RILEM Technical Committee 232-TDT, Test methods and design of textile  
434 reinforced concrete, *Mater Struct* 49 (12) (2016) 4923–4927.
- 435 [22] R. A. Fisher, *Statistical methods for research workers*, Oliver and Boyd,  
436 Edinburgh, 1925.
- 437 [23] D. Arboleda, *Fabric reinforced cementitious matrix (FRCM) composites for*  
438 *infrastructure strengthening and rehabilitation: Characterization methods*,  
439 *Ph.D. thesis, University of Miami, open Access Dissertation. Paper 1282*  
440 *(2014)*.
- 441 [24] C. Signorini, A. Nobili, A. Sola, M. Messori, Diluted  
442 epoxy-coatings for TRM composites: tensile tests raw data,  
443 <http://dx.doi.org/10.17632/kgb7dz3yhx.3>, , *Mendeley Data*, v3 (2019).
- 444 [25] G. Kaye, T. e. a. Laby, *Tables of physical and chemical constants and some*  
445 *mathematical functions*, Longmans, London, 1966.
- 446 [26] P. Good, *Permutation tests: a practical guide to resampling methods for*  
447 *testing hypotheses*, Springer Science & Business Media, 2013.

- 448 [27] Camera di Commercio di Modena, Building materials price datasheet  
449 2018 (prezziario opere edili 2018), [https://www.mo.camcom.it/tutela-del-](https://www.mo.camcom.it/tutela-del-mercato/prezzi/prezzi-informativi-delle-opere-edili-in-modena)  
450 [mercato/prezzi/prezzi-informativi-delle-opere-edili-in-modena](https://www.mo.camcom.it/tutela-del-mercato/prezzi/prezzi-informativi-delle-opere-edili-in-modena) (2019-06-  
451 20).
- 452 [28] CNR-DT 200 R1, Guide for the design and construction of an externally  
453 bonded FRP system for strengthening existing structures, Italian National  
454 Research Council, Rome, 2013.
- 455 [29] C. Signorini, A. Nobili, Effect of aggressive environment exposure on  
456 mechanical performance of Steel-FRCM and Textile Reinforced Concrete  
457 (TRC), in: Esculapio (Ed.), ICCS21 – 21st International Conference on  
458 Composite Structures, 2018.